



Ambient and Nitrogen Environment Friction Data for Various Materials & Surface Treatments for Space Applications


Azhar Vellore¹ · Sergio Romero Garcia¹ · Duval A. Johnson² · Ashlie Martini¹

Received: 11 August 2020 / Accepted: 10 December 2020 / Published online: 12 January 2021
© The Author(s), under exclusive licence to Springer Science+Business Media, LLC part of Springer Nature 2021

Abstract

A multivariate tribological evaluation of candidate materials, surface treatments and dry film lubricants is needed for design of moving mechanical components that function reliably in extreme conditions, including for long-duration space missions. In this study, linear reciprocating or unidirectional sliding friction data was collected using ball-on-flat tests. The balls were hardened 440C stainless steel (either uncoated or sputtered with MoS₂) and flat surfaces were 440C stainless steel, Nitronic 60 stainless steel or Ti6Al4V titanium alloy with various surface treatments and/or dry film lubricants. Surface treatments included anodizing, nitriding and electrical discharge machining. The dry film lubricants included Microseal 200-1, sputtered MoS₂ and a nano-composite coating i-Kote. The data contains applied normal load, measured friction force, calculated coefficient of friction, ball position, ambient temperature and relative humidity during testing. Tests were performed at different peak Hertzian contact pressure conditions ranging from 300 to 2000 MPa. Data is also available for flat surfaces that were vacuum baked at 150 °C after surface treatment and dry film coating as well as samples tested in inert gas (nitrogen) environment. This data can be used both to fundamentally understand the tribological properties of different material systems as well as to enable design of components for specific applications, conditions and duty cycles.

Graphical Abstract

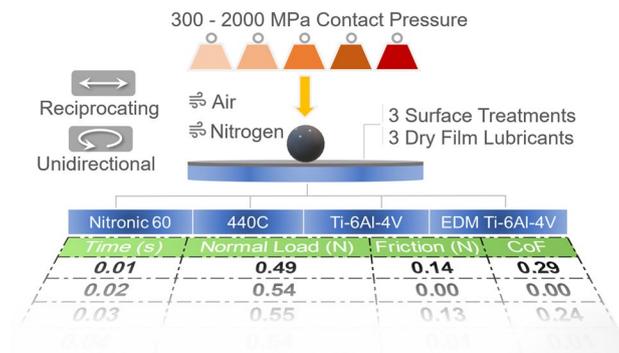

Keywords Friction data · Coefficient of friction · Dry film lubricant · Nitriding · Anodizing · Ti alloy · MoS₂ · Microseal · i-kote

✉ Ashlie Martini
amartini@ucmerced.edu

¹ Mechanical Engineering Department, University of California, 5200 Lake Road, Merced, CA 95343, USA

² NASA Jet Propulsion Laboratory, Laboratory of Applied Tribology, Pasadena, CA, USA

1 Objective

Mechanical components are designed to perform reliably throughout their operational life. Design is guided, in part, by the tribological properties of the materials used to produce them. Often, these materials undergo surface treatments to improve their mechanical properties and they may

Table 1 Surface treatments and dry film lubricants with the corresponding vendors

	Surface treatment	Dry film lubricant	Vendor
MS 200-1	–	Microseal 200-1	E/M Coating Services
i-Kote	–	i-Kote	Tribologix Inc
MoS ₂	–	Sputtered MoS ₂	Hohman Plating & Manufacturing Inc
Danco Type 2	Anodizing	–	Danco Anodizing
Tiodize Type II	Anodizing	–	Tiodize Co., Inc
Tiodize Type IV	Anodizing (with PTFE)	–	Tiodize Co., Inc


be coated with dry film lubricants for efficient operation, particularly in extreme conditions where liquid lubricants are not feasible [1].

Efficient operation is particularly critical in space applications where service or replacement of parts is not possible. For such applications, the tribological performance of various candidate materials, surface treatments and dry film lubricants have to be evaluated to identify optimal design strategies [2, 3]. Tribological performance evaluation involves sliding between different materials with various surfaces of interest and measuring the friction force. The change in coefficient of friction (CoF) over time during sliding can help identify the best candidate for a given set of operating conditions and duty cycles. Such data can also provide fundamental insight into the tribological behavior of various materials [4].

In this study, we collected friction performance data for different substrate materials including 440C stainless steel, Nitronic 60 stainless steel and titanium alloy (Ti6Al4V), sliding against 440C stainless steel ball (uncoated or sputter coated with MoS₂). Substrates underwent different surface treatments, including anodizing (with or without PTFE impregnation) nitriding and electrical discharge machining. Some were coated with dry film lubricants, including Microseal 200-1, sputtered MoS₂ and i-Kote. Corresponding vendor information is shown in Table 1. Some friction tests were performed in inert gas environment (nitrogen) or after baking the samples in vacuum at 150 °C for one hour.

2 Data Uniqueness

The data reported here was collected to study the performance of different types of surface treatments and dry film lubricants on various substrates in both ambient and inert gas environments for space applications. An inert gas environment is typically used as a proxy for the vacuum of space in tribological studies. Testing in inert gas entailed designing and fabricating a custom enclosure that was retrofitted on to the tribometer instrument with sensors to monitor ambient temperature, humidity and oxygen concentration. Data collection also involved fabrication of custom test specimen that were processed using a variety of commercially available techniques provided by multiple different companies and performing tribological experiments across a range of operating parameters and environments. Running such experiments, particularly with the material and surface treatments studied here, is both expensive and labor-intensive. This data may be valuable to anyone considering corrosion resistant, anti-galling surface treatments and tribologically superior dry film lubricants in their mechanical components, particularly for space applications.

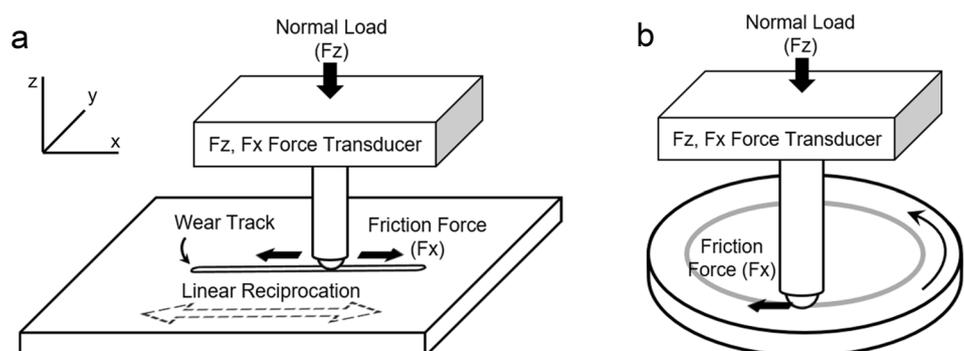Fig. 1 Schematics of the **a** ball-on-flat linear reciprocating test and **b** ball-on-disk unidirectional test

3 Methodology

3.1 Test Conditions

Tribological testing to measure friction and wear was performed using an Rtec Instruments Multifunction tribometer, modified to include a custom enclosure that enabled testing in inert gas environments. Linear reciprocating and unidirectional sliding tests were performed to measure CoF with ball-on-flat and ball-on-disk set-ups using modified ASTM G-133 and ASTM G99-17 standard procedures, shown schematically in Fig. 1a and b, respectively.

Most tests were performed at room temperature (22 °C) and ambient air conditions with relative humidity between 30 and 50% and some tests were performed in dry nitrogen environment at room temperature and relative humidity < 5% and oxygen concentration < 0.4%. The test parameters in the reciprocating tests were 10 mm stroke length, 0.5 mms⁻¹ sliding speed and applied loads corresponding to calculated peak Hertzian contact pressures of 300, 500, 800, 1100 and 2000 MPa. In the unidirectional tests, the sliding speed was 1000 mms⁻¹ at 300 MPa and 100 mms⁻¹ at 1100 MPa contact pressure.

3.2 Materials

Flat or disk specimens with different substrate materials and surface treatments were tested. The substrate was stainless steel (440C or Nitronic 60) or titanium alloy Ti6Al4V. The Ti6Al4V alloy was either machine cut (referred to as 'Ti6Al4V') or electrical discharge machining (EDM) cut (referred to as 'EDM Ti6Al4V'). Some surface and mechanical properties of these substrates are shown in Table 2. The surface roughness of the substrates before treatment or DFL coating was measured to be ~130 nm using contact-mode profilometry and the roughness of the tested surfaces (reported in the Overview spreadsheet) was measured using interferometry. The surface treatments included in this study were nitriding and anodizing, and the dry film lubricants tested were sputtered MoS₂, Microseal 200-1 or i-Kote. The anodized surfaces were fabricated by two different vendors Danco (Type 2 anodizing) or Tiodize (Type II and Type IV anodizing). Representative images of these samples are shown in Fig. 2.

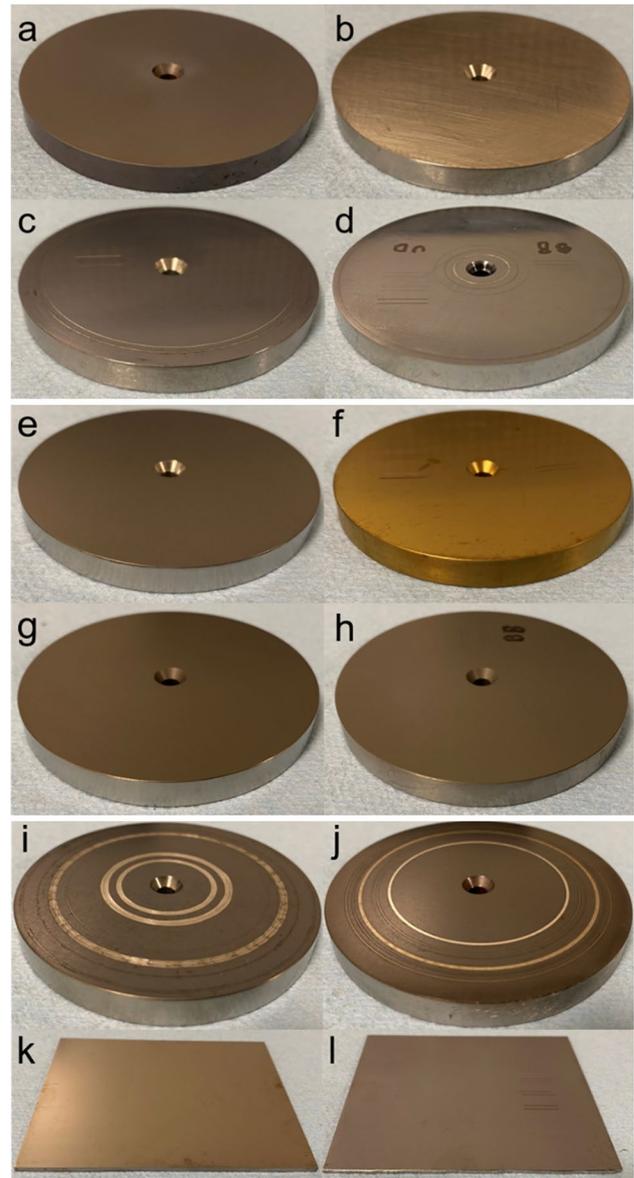


Fig. 2 Photos of the samples tested in this study: **a** 440C with MS 200-1, **b** Nitronic 60, **c** Nitronic 60 with MS 200-1, **d** EDM Ti6Al4V with MoS₂, **e** Anodized Ti6Al4V (Danco Type 2), **f** Nitrided Ti6Al4V, **g** Anodized Ti6Al4V (Tiodize Type II), **h** Anodized Ti6Al4V (Tiodize Type IV), **i** Ti6Al4V with i-Kote, **j** 440C with i-Kote, **k** Ti6Al4V, and **l** Ti6Al4V with MS 200-1

Table 2 Substrate material properties

Substrate	Rockwell hardness	Elastic modulus (GPa)	Poisson's ratio
440C	C45-50	200	0.28
Nitronic 60	B85	180	0.30
Ti6Al4V	C35	110	0.31
EDM Ti6Al4V	C35	110	0.31

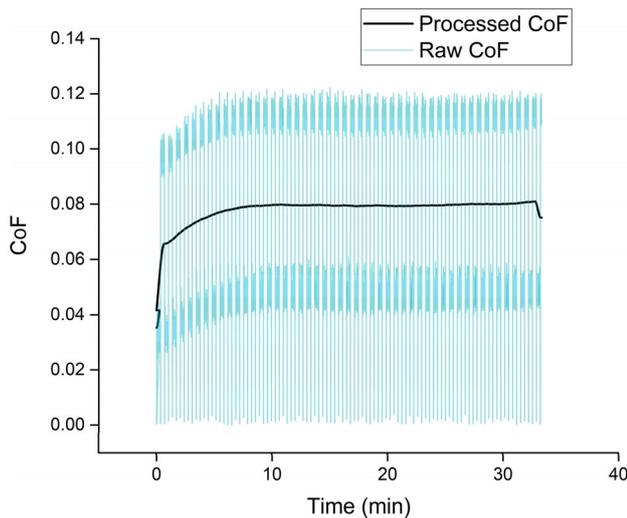


Fig. 3 CoF plot from a linear reciprocating test showing raw and processed data

440C stainless steel balls of diameter 4.76 mm (3/16 inch) or 9.53 mm (3/8 inch) and Rockwell C60 hardness (with and without sputtered MoS₂) were used as the counter-body.

3.3 Friction Data Processing

The available files contain raw (reciprocating and unidirectional tests) and post-processed (reciprocating tests) data. Post-processing was done in the case of reciprocating tests to correct for friction force bias that occurs due to misalignment between the force transducer and the sample surface. This misalignment is typically a result of changes in surface topography during sliding or machining imperfections. Misalignment induced friction force measurement uncertainties can be minimized by averaging the absolute friction force from the forward and backward motion of the ball on the sample [5]. Averaging and data smoothing was accomplished using a moving mean and Bartlett window [6] size of ~8000 data points with a boundary handler. Although the Bartlett window function can result in discontinuities at the beginning and end of the data, the general CoF trend is not affected, as shown in the example in Fig. 3.

4 Data Description

The data sets contain applied normal load, measured friction force, calculated CoF, position of the ball, ambient temperature and relative humidity during testing. The column headers corresponding to each parameter are listed below in the order of appearance in the data file.

1. Step – Tribometer program step
2. Timestamp – Time of recording of data
3. RecipeStep – Tribometer program step
4. DAQ.Fz (N) – Normal load in N
5. DAQ.Fx (N) – Friction force in N
6. DAQ.COFA () – Coefficient of friction
7. XYZ.X Position (mm) or Rotary.Position (rev) – Absolute position of ball along the wear track in mm (for reciprocating tests) or absolute angular displacement of the flat disk in terms of number of revolutions (for unidirectional tests)
8. RTC.Temperature (°C) – Ambient temperature in degrees Celsius
9. RTC.RH (%) – Relative humidity of ambient air

Headers ‘Step’ and ‘RecipeStep’ (1 and 3) both refer to the programming step the tribometer is executing at the time of recording. For example, the reciprocating sliding tests were performed by the tribometer in two steps. In the 1st step, the ball was moved towards the substrate until the desired normal load was attained. In the 2nd step, sliding was performed, and the friction force was measured. So, the COF data in the Step/RecipeStep 1 is to be disregarded for sliding friction performance. Similarly, the unidirectional tests were performed in two steps: Step 1 was rotating the disk at set RPM and Step 2 was loading the ball. However, note that only Step 2 data was recorded in unidirectional tests. Header ‘Timestamp’ starts from zero in each step and represents the time in seconds at which the data was recorded. Headers with ‘DAQ’ prefix (4,5 and 6) correspond to normal force (Fz), friction force (Fx) and CoF measured and calculated from the force sensors. Header ‘XYZ.X’ (7), only present in case of linear reciprocating tests, refers to the absolute position of ball along the wear track at any given

Table 3 Overview of data files grouped by substrate material

Label	Name of data file/data set	File extension	Data repository and identifier (DOI or accession number)
File 1	Overview.xlsx	.xlsx	https://doi.org/10.6071/M33M4Q
Data Set 1	Nitronic60.zip	.zip	https://doi.org/10.6071/M33M4Q
Data Set 2	440C.zip	.zip	https://doi.org/10.6071/M33M4Q
Data Set 3	Ti6Al4V.zip	.zip	https://doi.org/10.6071/M33M4Q
Data Set 4	EDM Ti6Al4V.zip	.zip	https://doi.org/10.6071/M33M4Q

time. The difference between the minimum and maximum values of the absolute position is the stroke length. The rate of change of the ball position can be used to calculate the instantaneous sliding speed. Header 'Rotary.Position (rev)' (7), only present in case of unidirectional sliding tests, refers to the absolute angular displacement of the test specimen (disk) in terms of number of revolutions. Note that XYZ.X Position and Rotary.Position do not always start at zero. Lastly, headers 'RTC.Temperature' and 'RTC.RH' refer to temperature (in degrees Celsius) and relative humidity (%) of the testing environment, respectively.

The sampling frequency of the force sensor was approximately 1000 Hz; however, every 10 points were averaged resulting in an effective sampling frequency of 100 Hz. The raw unfiltered data along with the processed data is stored as comma delimited data in CSV format files. Data files corresponding to different substrate materials and surface treatments are combined into data sets as shown in Table 3.

4.1 Limitations

- In most cases, there are only two test repetitions and, in few cases, three.
- Not all pressure conditions were tested for all material/surface treatment/dry film lubricant cases.
- In a few tests, temperature data was not collected, and the temperature is shown as '-999'.
- Wear data was not captured in this study.

5 Vendor contact information pertaining to dry film lubricants and surface treatments

1. Tiodize Co., Inc.
5858 Engineer Drive, Huntington Beach, California, USA 92649
Tel: + 17148984377 Website: www.tiodize.com
2. Danco Anodizing
44 LA Porte St., Arcadia, California, USA 91006
Tel: + 16264453303 Website: www.danco.net
3. E/M Coating Services (Parent company: Curtiss-Wright Surface Technologies)
20,751 Superior Street, Chatsworth, California, USA 91311

Tel: + 18184076280 Website: <https://cwst.com>

4. Hohman Plating & Manufacturing Inc.
814 Hillrose Ave, Dayton, Ohio, USA 45404
Tel: + 19372282191 Website: <https://hohmanplating.com>
5. Tribologix Inc
1440 Brickyard Road, Unit 4, Golden, Colorado, USA 80403
Tel: + 13032782211 Website: <https://tribologix.com>

Acknowledgements This research was supported by the NASA Merced nAnomaterials Center for Energy and Sensing (MACES) through the support of the National Aeronautics and Space Administration (NASA) Grant No. NNX15AQ01. A portion of this research was carried out at the Jet Propulsion Laboratory, California Institute of Technology and was sponsored by NASA (80NM0018D0004). Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise, does not constitute or imply its endorsement by the United States Government or the Jet Propulsion Laboratory, California Institute of Technology.

Data Availability The data described in this data note can be freely and openly accessed on DRYAD (<https://datadryad.org>). Please see Table 3 for details and links to the data.

References

1. Donnet, C., Erdemir, A.: Historical developments and new trends in tribological and solid lubricant coatings. *Surf. Coat. Technol.* **180-181**, 76–84 (2004). <https://doi.org/10.1016/j.surfcoat.2003.10.022>
2. Lince, J.R.: Effective application of solid lubricants in spacecraft mechanisms. *Lubricants* **8**, 74 (2020). <https://doi.org/10.3390/lubricants8070074>
3. Briscoe, H.M.: Why space tribology? *Tribol. Int.* **23**, 67–74 (1990). [https://doi.org/10.1016/0301-679X\(90\)90040-V](https://doi.org/10.1016/0301-679X(90)90040-V)
4. Vellore, A., Romero Garcia, S., Walters, N., Johnson, D.A., Kennett, A., Heverly, M., Martini, A.: Ni-doped MoS₂ dry film lubricant life. *Adv. Mater. Interfaces* **7**, 2001109 (2020). <https://doi.org/10.1002/admi.202001109>
5. Burris, D.L., Sawyer, W.G.: Addressing practical challenges of low friction coefficient measurements. *Tribol. Lett.* **35**, 17–23 (2009). <https://doi.org/10.1007/s11249-009-9438-2>
6. Bartlett, M.S.: Periodogram analysis and continuous spectra. *Biometrika* **37**, 1 (1950). <https://doi.org/10.2307/2332141>

Publisher's Note Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.